

# *Effect Of Sludge On Properties Of Concrete By Partial Replacement Of Fine Aggregate*

Mr.Rahul K.Hon<sup>1</sup>

PG Scholar, Department of Civil Engineering, D.V.V.P.  
College of Engineering, Ahmednagar,  
Maharashtra.  
Email id-rahul.hon123@gmail.com

Prof. S.N.Daule<sup>2</sup>

PG Guide, Department of Civil Engineering,  
D.V.V.P.College of Engineering, Ahmednagar,  
Maharashtra.  
Email id-shashirdaule@gmail.com

## **ABSTRACT**

*To evaluate the effect of dry sludge on concrete performance, its mechanical properties were studied.*

*The rapid increase in construction activities leads to scarcity of conventional construction materials such as cement, fine aggregate and coarse aggregate. Researches are being conducted for finding cheaper materials. In India, there are many water treatment plant WTP sludge which leads in problems of disposal. The final destination of water treatment treatment plant sludge affects the environment.*

*In this research an attempt is taken by partial replacement of fine aggregate into WTP sludge in various proportions so that the final product property of concrete mixture is same as the conventional mix. Water treatment plant sludge material was replace with fine in various percentages such as 0%, 5%, 10% & 15% reasons.*

**Keyword :** - WTP sludge coarse aggregate compressive strength flexural strength split tensile strength

## **I INTRODUCTION**

Concrete is material composed of aggregates bonded together with fluid cement which hardens over time. It is the world's most widely used building material having properties such as fire resistance, durability, strength, maintenance free, easy installation, low installation cost, high compressive strength, custom design flexibility etc. Sludge a hazardous waste produced from purifying water has been identified as a potential alternative ingredient in making concrete. Using sludge in concrete could have an impact on cost, as well as protect the environment from its detrimental effects. The increasing population of India has increased the demand for potable water. This sludge can be used in the concrete by controlling the chemical proportionality of the sludge. Considering the field of construction is one of the biggest consumers of base materials, the recycling of sludge for the concrete could decrease the environmental problems of sludge disposal significantly, while also replacing the necessity for base materials in the process. The concrete industry uses a considerable amount of natural

resources to produce cement and concrete. The drawbacks of conventional concrete may also include its high self weight which makes it to some extent an uneconomical structural material. Water treatment sludge is replace with fine aggregate in various percentages such as 0%, 5%, 10% & 15.

## **II LITERATURE REVIEW**

**M. Silva and T. R. Nark (2010)** Studied on sustainable use of resources, such as use of reclaimed water, especially partially processed Water treatment plant water in concrete. A initial laboratory investigation was conduct samples were collected from the Milwaukee Metropolitans various District and analyzed the Characteristics of wastewater.

**Prof V. P. Bhargava(2016)** Several experiments using alum sludge in brick making had been reported in many countries. Patricia et al.conducted ceramic brick manufacturing from drinking water treatment plants. They carried out experiments to get a sand replacement by 10% of sludge and this percentage is considered appropriate for ceramic brick. It indicated an interesting potential for reuse alum sludge as construction material.

**R.A. More and S.K. Dubey (2014)** Studied on effect of different types of water on compressive strength of concrete. They made concrete cube with mineral water, WTP water, well water and waste water increased with days & not having much variation in their compressive strength. The concrete mix of M20 grade with water cement ratio of 0.5 was investigated.

## **III OBJECTIVES OF INVESTIGATION**

1 To study the utilization of sludge by Compressive and split tensile and Flexural strength of Concrete by replacement of fine aggregate.

2 Utilization of Sludge will reduce the excess use of sand in environment

3 Utilization of WTP sludge reduce the Pollution of land .

## **IV MATERIAL.**

A.Cement Test Result



*Dr. V. P. Bhargava*  
PRINCIPAL  
Dr Vithalrao Vikhe Patil  
College of Engineering  
Ahmednagar

Table no 2 Test value of cement

|        |                             |                        |
|--------|-----------------------------|------------------------|
| Cement | Bulk density                | 1400 kg/m <sup>3</sup> |
|        | Specific Gravity            | 3.15                   |
|        | Initial Setting Time        | 120                    |
|        | Final Setting Time          | 170                    |
|        | Le-Chatelier Soundness test | 1%                     |
|        | Fineness Of Cement          | 0.70                   |

## B. Aggregate Test Result:

Table no 3 Test value of Aggregate

| Properties       | Coarse. Aggregate | Coarse. Aggregate | Fine Aggregate  | WTP Sludge      |
|------------------|-------------------|-------------------|-----------------|-----------------|
| Type             | Crushed Angular   | Crushed Angular   | Crushed Angular | Crushed Regular |
| Max Size         | 20mm              | 10                | 4.75            | 4.75            |
| Fineness Modulus | 2.55              | 2.51              | 2.77            | 2.20            |
| Sp.Gravity       | 2.70              | 2.65              | 2.63            | 1.08            |
| Water Absorption | 1.35%             | 1.2%              | 0.7%            | 0.72%           |
| Impact Value     | 12.73%            | 13.16%            | --              | --              |
| Crushing Value   | 25%               | 28.8%             | --              | --              |

## V. METHODOLOGY

## A. SLUDGE

Sludge was collected from Vaijapur for mixing and curing as per IS 456:2000.

The Sludge were dried in Oven at 100 degree C for 3 hours and then used as replacement with fine aggregate

## B. FINE AGGREGATE:

Locally available natural river sand is used confirming to IS 383-1970. Properties of aggregate are as shown in table no 3.

## C. COARSE AGGREGATE

The aggregate of size 20mm were used confirming to IS 383-1970. Properties of aggregate are as shown in table no 3

Table no 4 Summary of Concrete Mix Design

| Material used for Concrete |                          |
|----------------------------|--------------------------|
| Grade Designation          | M 30                     |
| Type of Cement             | OPC 53                   |
| Maximum Size of aggregates | 20 mm                    |
| Minimum Concrete content   | 400.00 Kg/m <sup>2</sup> |
| Maximum Water Cement Ratio | 0.45                     |
| Exposure Condition         | Severe                   |
| Method of Concrete Placing | Manual                   |
| Degree of Supervision      | Good                     |
| Type of Aggregate          | Crushed Angular          |

## A. Concrete Mix Design

Mix design is a process of selecting suitable ingredients for concrete mixes and to determining their proportions which would finding out , as economically as possible, a concrete that satisfies the requirements. The proportion of the ingredients of concrete is an important phase of concrete technology as it ensures quality and economy of construction work.

In pursuit of the goal of obtaining concrete with desired performance characteristics, the selection of component materials is the first step, the next step is a process called mix design by which one arrives at the right combination of the ingredients. There are many methods of designing concrete mixes. In this research concrete mix design was done for both group of concrete separately.

## B.Mix Design For Grade M 30:

## Design Steps

Step 1: Target Mean Strength For the degree of quality control specified namely "Good" the value of standard deviation is,  $\sigma = 4.0 \text{ N/mm}^2$  (I.S: 10262-2009). Hence the targeted mean strength for the desired compressive strength  $f_{ck} = f_{ck} + 1.65 \times s$  - IS 10262 Table 1 =  $30 + (1.65 \times 5.0) f_{ck} = 38.25 \text{ N/mm}^2$ .

Step2: Selection of Water Cement Ratio from Table 5 of IS 456 – 2000 Maximum water-cement ratio is 0.5.

Step 3: Selection of Water content Size of maximum aggregate =20 mm Maximum volume of water = 197 liters considering (trial): 180 liters

Step4: Selection of Cement content Water cement ratio: 0.5  
Cement content =  $180/0.4 = 400.00 \text{ kg/m}^3$ ,  $400.00 \text{ kg/m}^3 > 320 \text{ kg/m}^3$  minimum cement content for mild exposure. Therefore OK

Step5:Proportion of the Volume of fine Aggregate and coarse Aggregate Content From Table no 3 volume of coarse aggregate corresponding to 20 mm size aggregate and fine aggregate for water cement ratio of 0.45 =0.60 As per our experience we considered water cement ratio as 0.45 and for that we made no change in value and no effect of pump able concrete to be provided. Therefore volume of coarse aggregate required = 0.60  
Volume of fine aggregate:  $1 - 0.60 = 0.40$

Step6: Mix Calculation


## VI. RESULTS

### A.Slump Cone Test-

Slump Cone test was conducted for investigation of workability of fresh concrete. Fine aggregate replaced with 0%, 5%, 10% ,15%.

Table no-5 Slump Cone Test

| Mix design | Slump values in mm |
|------------|--------------------|
| 0% sludge  | 80                 |
| 5% sludge  | 76                 |
| 10% sludge | 74                 |
| 15% sludge | 68                 |

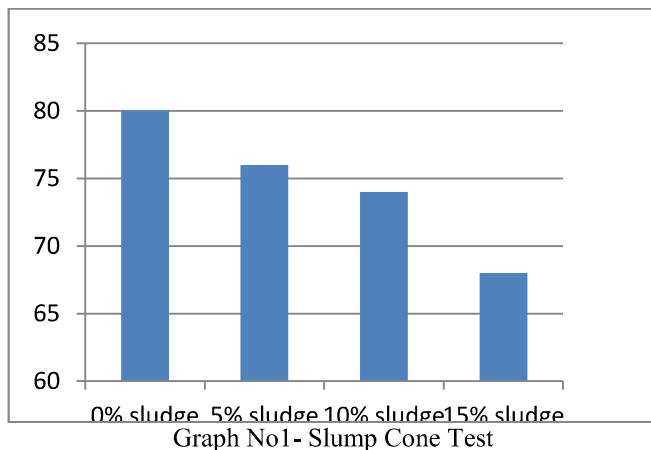


### B.Compressive Strength

A cube compression test was performed on standard cubes of GPC of size 150mm x 150mm x 150 mm after 7 days, 14 days and 28 days after ambient curing.



Table no-6 Compressive Strength Of Concrete

| Sr No       | 1                | 2                | 3                 | 4                 |
|-------------|------------------|------------------|-------------------|-------------------|
| % OF Sludge | 0%Sludge Avg Mpa | 5%Sludge Avg Mpa | 10%Sludge Avg Mpa | 15%Sludge Avg Mpa |
| 7 DAY       | 24.6             | 23.7             | 21                | 18.9              |
| 14DAY       | 26.8             | 25.5             | 24.7              | 23.3              |
| 28DAY       | 42.50            | 41.30            | 39.30             | 38.10             |

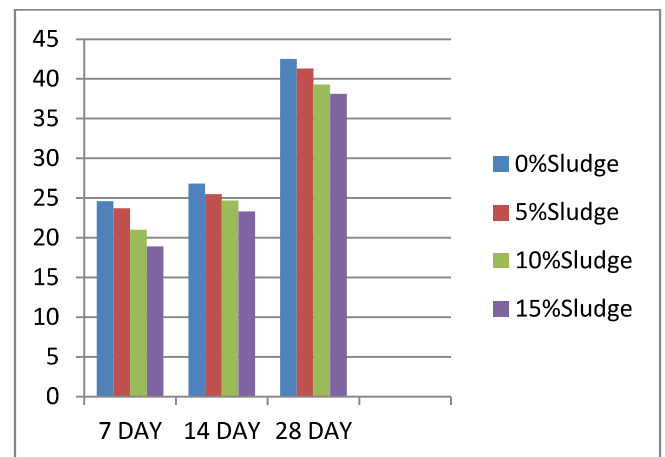


Graph no2- Compressive Strength Of Concrete

### C.Split Tensile Test.

The split tensile test conducted on cylinders of 150mm dia.x300mm height. Split tensile strength of cylinder specimens is determined by placing between the two plates of Compression Testing Machine.

Table no-7 Split Tensile Test Of Concrete

| Sr No     | 28day Avg(Mpa) |
|-----------|----------------|
| 0%Sludge  | 5.76           |
| 5%Sludge  | 5.00           |
| 10%Sludge | 4.63           |
| 15%Sludge | 4.21           |

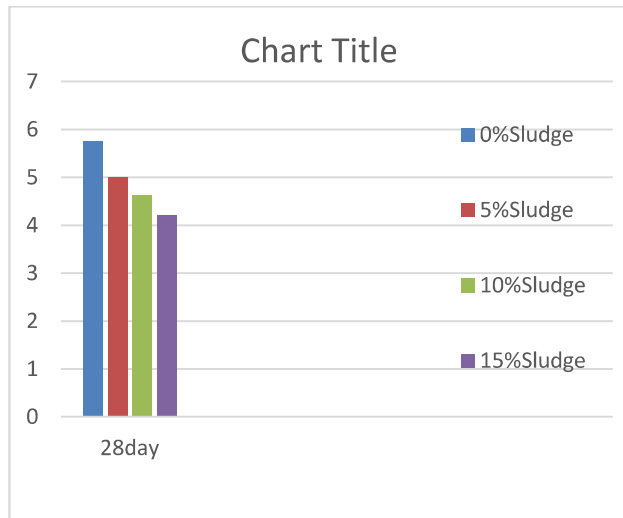


Graph no3- Split Tensile Test Of Concrete

### D.Flexural Test

In flexural test, the Standard beam specimen of size 100mm x 100mm x 500mm were supported symmetrically over a span of 400mm in the machine in such a manner at the load is applied uppermost surface as cast in the mould.

Table no-8 Flexural Test

| Sr No           | 0%<br>Sludge | 5%<br>Sludge | 10%<br>Sludge | 15%<br>Sludge |
|-----------------|--------------|--------------|---------------|---------------|
| 28day           | 11.65        | 10.95        | 9.75          | 8.4           |
|                 | 11.8         | 11.00        | 9.8           | 8.25          |
|                 | 12.20        | 10.95        | 9.85          | 8.45          |
| Avg value (MPA) | 11.80        | 10.96        | 9.80          | 8.36          |

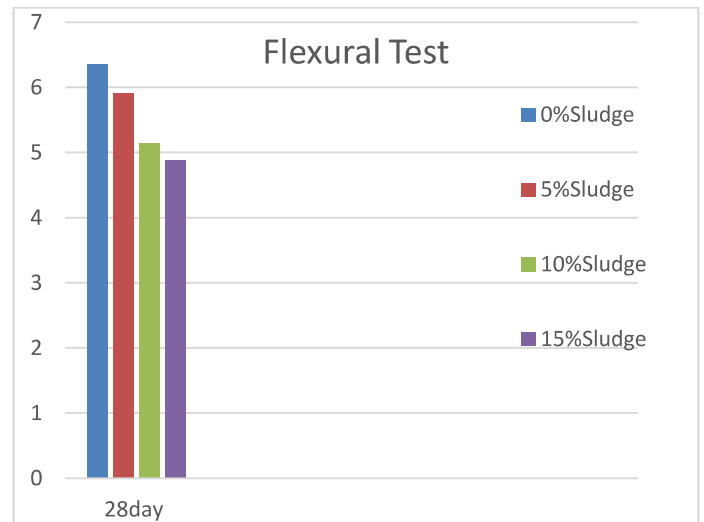

Graph no 4- Split Tensile Test Of Concrete

### E .Rebound Hammer Test (IS: 13311 (Part 2) – 1992).


Rebound hammer test is used to be finding the compressive strength of concrete members. It is consists of every rebound spring control hammer that slides on a plunger within the tubular housing. After impact the hammer rebounds. The distance traveled by mass, is called as rebound number.



Rebound Hammer Test

Table No- 9 Rebound Hammer Test

| SR.NO     | 28DAY ,MPA |       |       | AVG   |
|-----------|------------|-------|-------|-------|
| 0%Sludge  | 49.4       | 49.5  | 48.9  | 49.26 |
| 5%Sludge  | 47.9       | 47.85 | 48.10 | 47.95 |
| 10%Sludge | 45         | 44.9  | 45.2  | 45.00 |
| 15%Sludge | 42.6       | 42.4  | 41.9  | 42.3  |

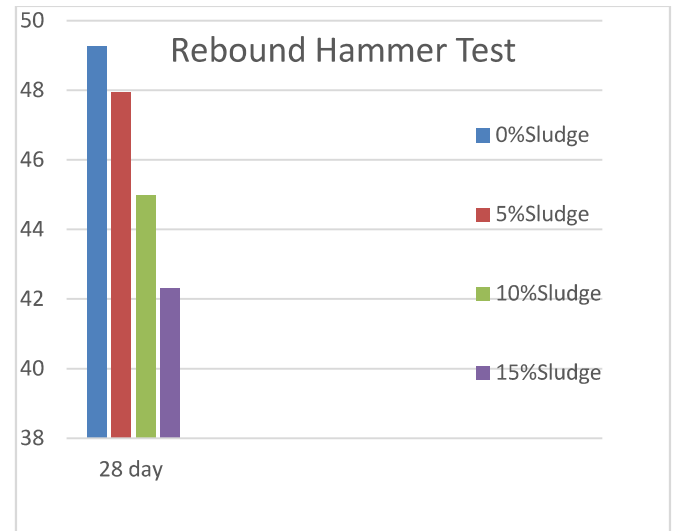

Graph no5- Rebound Hammer Test

## VII.CONCLUSION

1. Strength of 5 % replaced sludge concrete is increased compared with 10, 15 % of concrete. The compressive strength of concrete is showing better results up to 10 % sludge replacement with fine aggregate.
2. According to results it is not suitable for structural element so used for the paving blocks and for footpath as a non structural element.
3. Application of Dry Sludge replace as Fine Aggregate in Concrete With 0%, 5%, 10% & 15%. Producing concrete specimen at w/c ratio of 0.45, with 30% of dry sludge was impossible due to very low workability.
4. Compressive strength of concretes containing dry sludge (w/c ratio of 0.55) Compressive strength of concretes containing dry sludge (w/c ratio of 0.45) It was observed that the dry sludge of waste water treatment plant in Vijapur city has a satisfying the dry sludge due to low pozzolanic activity, acts as filler or fine aggregate in concrete.
5. Utilization of 10% of dry sludge in concrete caused 8% decrease in compressive strength which was much lower than the decrease amounts reported in previous researches (about 42%). On the basis of results, it is proposed to use concretes containing more than 10% of dry sludge as non-structural concretes such as paving and flooring concretes.

## ADVANTAGES

- Decrease the water pollution.
- Reduce the use of fine aggregate.
- Well management of solid waste.
- Achieve economy.

## DISADVANTAGES

- Dose not takes heavy load.
- It is not use for tension member.
- Activated sludge not easily available in rural area.

- The odors of sludge are very bad.
- Sludge should not be used in **RCC** due to corrosion

#### VIII.ACKNOWLEDGEMENT

I am honored to express my deep sense of gratitude towards my guide Prof. S. N. Daule, Asst. Prof, Department of Civil Engineering, for his creative suggestions, helpful discussion, unfailing advice, constant encouragement during the project work., I express my sincere gratitude to Prof. S. L.Hake ME CO-Ordinator And U.R.Kawade HOD In Civil Department. I am indebted to my Parents, Friends and my colleagues for their support.

#### IX.REFERENCES

1. K. Nirmalkumar and V. Sivkumar (2008) Study on the durability of concrete by using recycled waste water sludge. Journal of industrial pollution control. pp 1-8
2. R. A. Taha (2010) the feasibility of using Ground (brackish) water and Production (oily) water in construction compared with Tap water. International Journal of sustainable water and environmental system. Vol. 1 39-43.
3. M. Silva and T. R. Naik (2010) sustainable use of resources. Second international conference construction material.
4. K. S. Al jabri (2011) the effect of waste water on properties of high strength concrete. Twelfth East Asia-Pacific conference on Structural Engg.
5. V. Kulkarni (2014) Study on compressive strength of concrete by using treated domestic waste water as mixing and curing of concrete. International Journal of Research in Engg. And Technology.
6. R.A. More and S.K. Dubey (2014) Study on effect of different types of sludge water on compressive strength of concrete. International Journal of Research in Engg. And Technology. 40-50
7. F. Adeyemiand (2014) Experimental investigations on the effect of sea water on the compressive strength of concrete. International Journal of Engg. Science Invention. 2321-0613
8. N. Reddy (2015) Use the Treated domestic waste water as mixing water in cement mortar. International Journal of Engg. Science Invention. PP 23-31
9. E.W. Gadzama (2015) Study on the effect of using sugar factory waste water as mixing water on the properties of normal strength concrete. International Journal of Science, Environment. 813-825
10. Shetty, M.S.Concrete technology – theory and practice. 5th ed. S. Chand and Co. Ltd., Ram agar, New Delhi, India, 2004
11. IS-456 - 2000-Plain and Reinforced Concrete Code of Practice
12. IS-516-1959 -Methods of tests for Strength of concrete.
13. IS-12269 - 1987- Specifications for 53 grade OPC.
14. IS 2386 (Part 1, 3 & 4) - 1963, Method of testing of aggregates for concrete.
15. IS 1199-1959 - Method of sampling and analysis of concrete.
16. IS 7320-1974 - Specification for concrete slump test apparatus?
17. IS 5816-1970- Method of test for split tensile strength of concrete cylinders
18. IS 579-1959 - Method for strength of concrete?
19. IS 10262-2009 - Recommended guidelines for mix design?